


Australian Wool Testing Authority Ltd - trading as AWTA Product Testing A.B.N 43 006 014 106 1st Floor, 191 Racecourse Road, Flemington, Victoria 3031 P.O Box 240, North Melbourne, Victoria 3051 Phone (03) 9371 2400 Fax (03) 9371 2499

## **TEST REPORT**

Client :	Gerflor Australasia Pty Ltd 17 Cato Street Hawthorn East VIC 3123			Test Number Issue Date	:	16-00163 28/04/201	
				Print Date	: 16/05/20		6
Sample Description		Clients Ref : "Texline HQR"					
		Timber effect vinyl flooring Colour : Timber					
		Nominal Composition : PVC/Fibreglass/Textile backing Nominal Thickness : 3.1mm					
		Radiant Heat Source					
		Date of Sample Arrival 31/03/2016					
		Date Tested 28/04/2016					
		CHF Value	1	2 3	6	Mean	
		Length	7.4	8.5 8.0	)	8.0	kW/m²
		Width	10.0	-	-	-	kW/m²
		Smoke Value	1	2 3		Mean	
		Length	106	96 119	)	107	%.min
		Width	59	-	-	-	%.min
		Penetration of flame through to substrate Yes					
		The test results relate to the behaviour of the test specimens of a product under the particula					
		conditions of the test, they a hazard of the product in use		ole criterion for assess	ing t	ne potential	tire

Sample was conditioned in accordance with BSEN 13238:2001 at a temperature of 23±2°C and relative humidity of 50±5% for a minimum of 48 hours prior to testing.

Each specimen was adhered to a substrate of 6mm thick fibre reinforced cement board using Roberts 656 adhesive and clamped prior to testing.

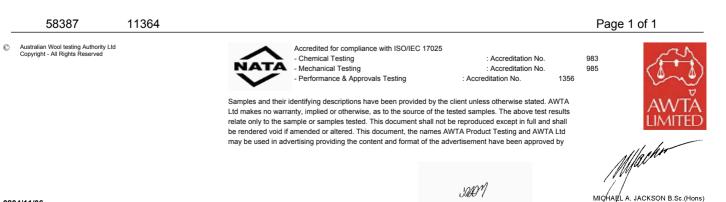

MANAGING DIRECTOR

A